




Email: [customerservice@fusion-chemical.com](mailto:customerservice@fusion-chemical.com)

Website: [www.fusion-chemical.com](http://www.fusion-chemical.com)

## Fusion Quench 15 @ 15%

<b>Test Reference</b>	Fusion Quench 15 @ 15%	<b>Manufacturer</b>	Fusion Chemical
<b>Operator</b>	123	<b>Formulation</b>	N/A
<b>Time of Test</b>	15:12:22	<b>Batch Number</b>	N/A
<b>Date of Test</b>	Apr-3-2018	<b>Type of Media</b>	Oil
<b>Type of Test</b>	Media	<b>Test Condition</b>	Static
<b>Test Start Temp</b>	1562 F	<b>Probe Number</b>	2467-7
<b>Media Temp</b>	104 F		
<b>Agitation Flowrate</b>			
<b>Comments</b>	Viscosity, SUS, @ 100 F...37.6 (D-445)		

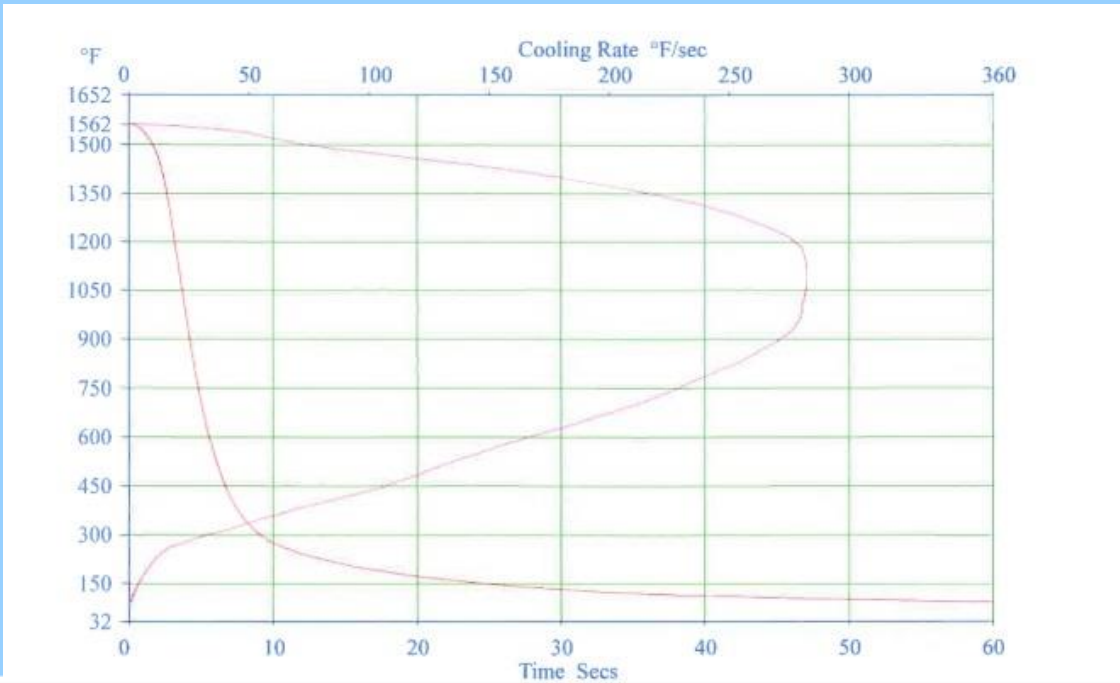

	Value	Minimum	Maximum	
Maximum Cooling Rate	282.61	.0	.0	°F/sec
Temp at Maximum Cooling Rate	1107.73	32	32	°F
Temp at Start of Boiling Phase				
Time at Start of Boiling Phase				
Temp at End of Boiling Phase				
Time at End of Boiling Phase				
Temp Diff between Start & End				
Cooling Rate at 572 °F	161.77	-1.8	-1.8	°F/sec
Cooling Rate at				
Cooling Rate at				
Time to reach 1112 °F	3.375	-1.000	-1.000	secs
Time to reach 752 °F	4.750	-1.000	-1.000	secs
Time to reach 392 °F	7.250	-1.000	-1.000	secs
Time from to				